

Taresco, Vincenzo and Suksiriworapong, Jiraphong and Creasey, Rhiannon and Burley, Jonathan C. and Mantovani, Giuseppe and Alexander, Cameron and Garnett, Martin (2016) Properties of acyl modified poly(glycerol-adipate) comb-like polymers and their self-assembly into nanoparticles. *Journal of Polymer Science Part A: Polymer Chemistry*, 54 (20). pp. 3267-3278.
ISSN 1099-0518

Access from the University of Nottingham repository:

<http://eprints.nottingham.ac.uk/42903/2/Supplementary%20info%20J%20polym%20Sci.pdf>

Copyright and reuse:

The Nottingham ePrints service makes this work by researchers of the University of Nottingham available open access under the following conditions.

This article is made available under the Creative Commons Attribution licence and may be reused according to the conditions of the licence. For more details see:
<http://creativecommons.org/licenses/by/2.5/>

A note on versions:

The version presented here may differ from the published version or from the version of record. If you wish to cite this item you are advised to consult the publisher's version. Please see the repository url above for details on accessing the published version and note that access may require a subscription.

For more information, please contact eprints@nottingham.ac.uk

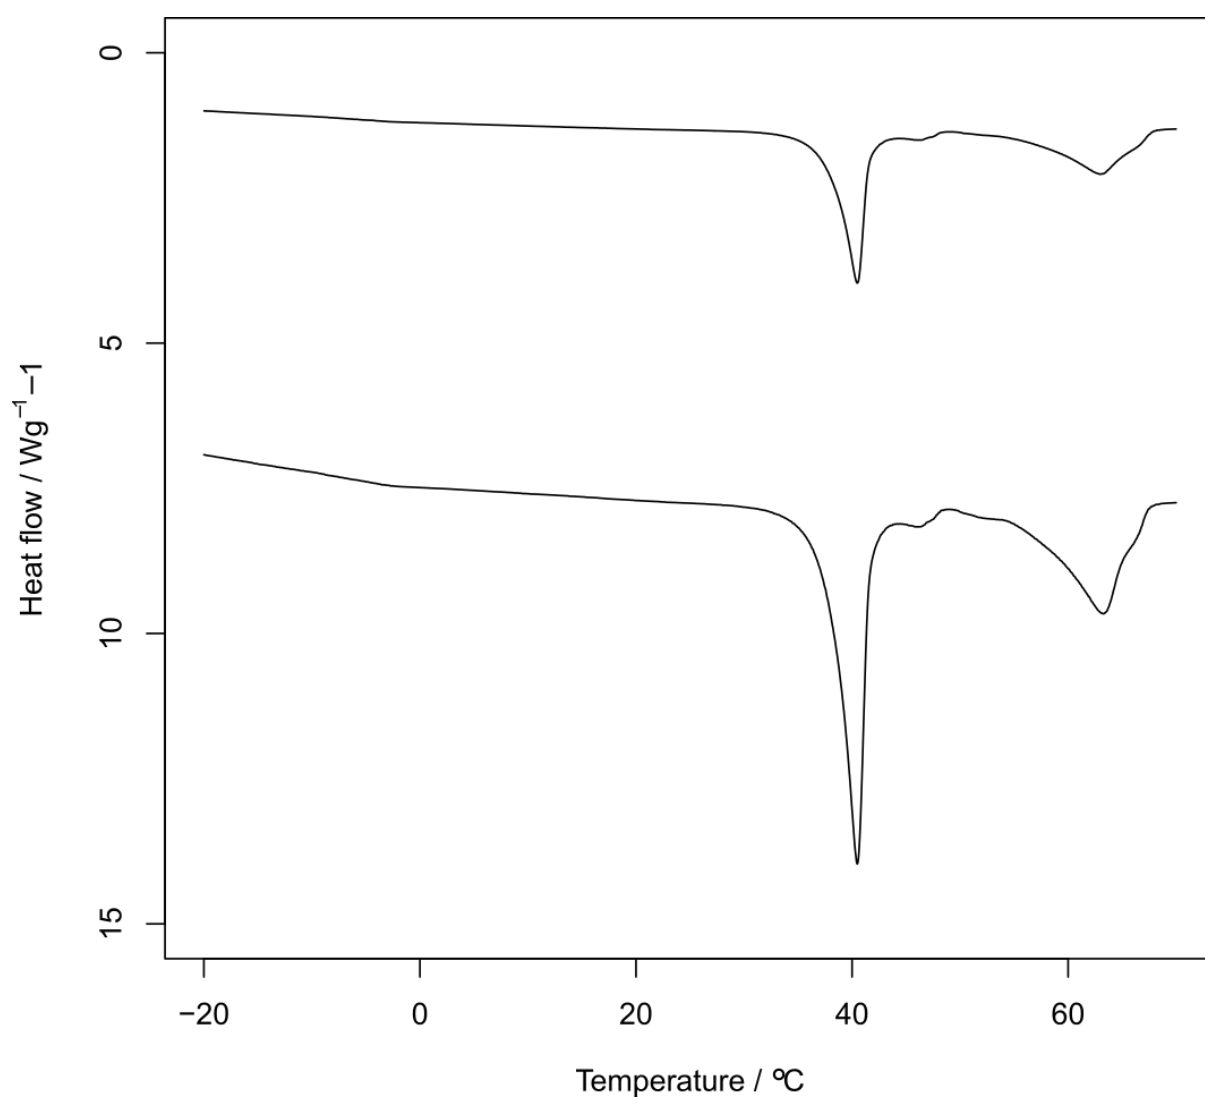


Figure SI1. Two thermograms of PGAS85 in the range between -20 and 70 °C. The two main melting transitions are present in both the thermal cycles.

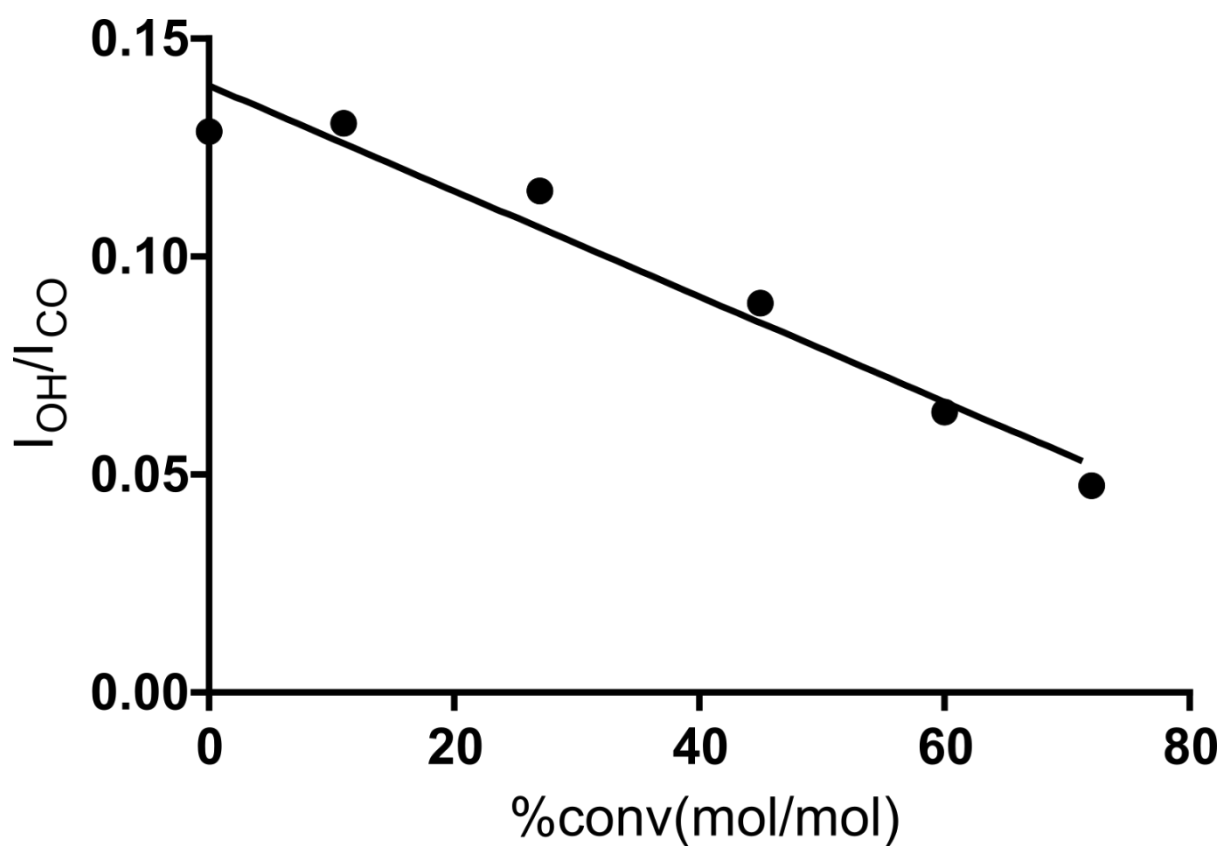


Figure S12. Ratio between the intensity of hydroxyl group stretching and the carbonyl group stretching decreases with the degree of functionalization. This particular graph depicts PGAB polymer set trend.

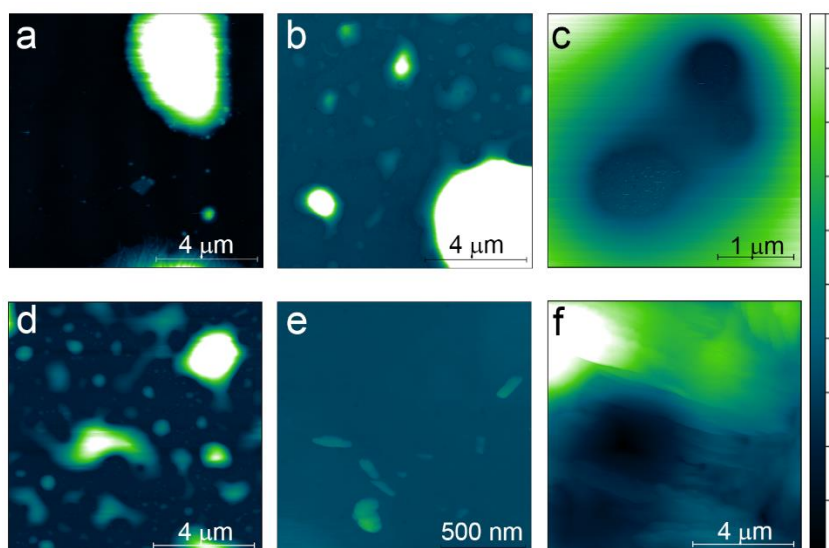


Figure SI3. AFM height images [with scale bars: x, z] of (a) PGA [4 μm , 100 nm], (b) PGAB 11% [4 μm , 100 nm], (c) PGAB 60% [1 μm , 100 nm], (d) PGAB 75% [4 μm , 100 nm], (e) PGO 65% [500 nm, 100 nm], and (f) PGAS 65% [4 μm , 800 nm].

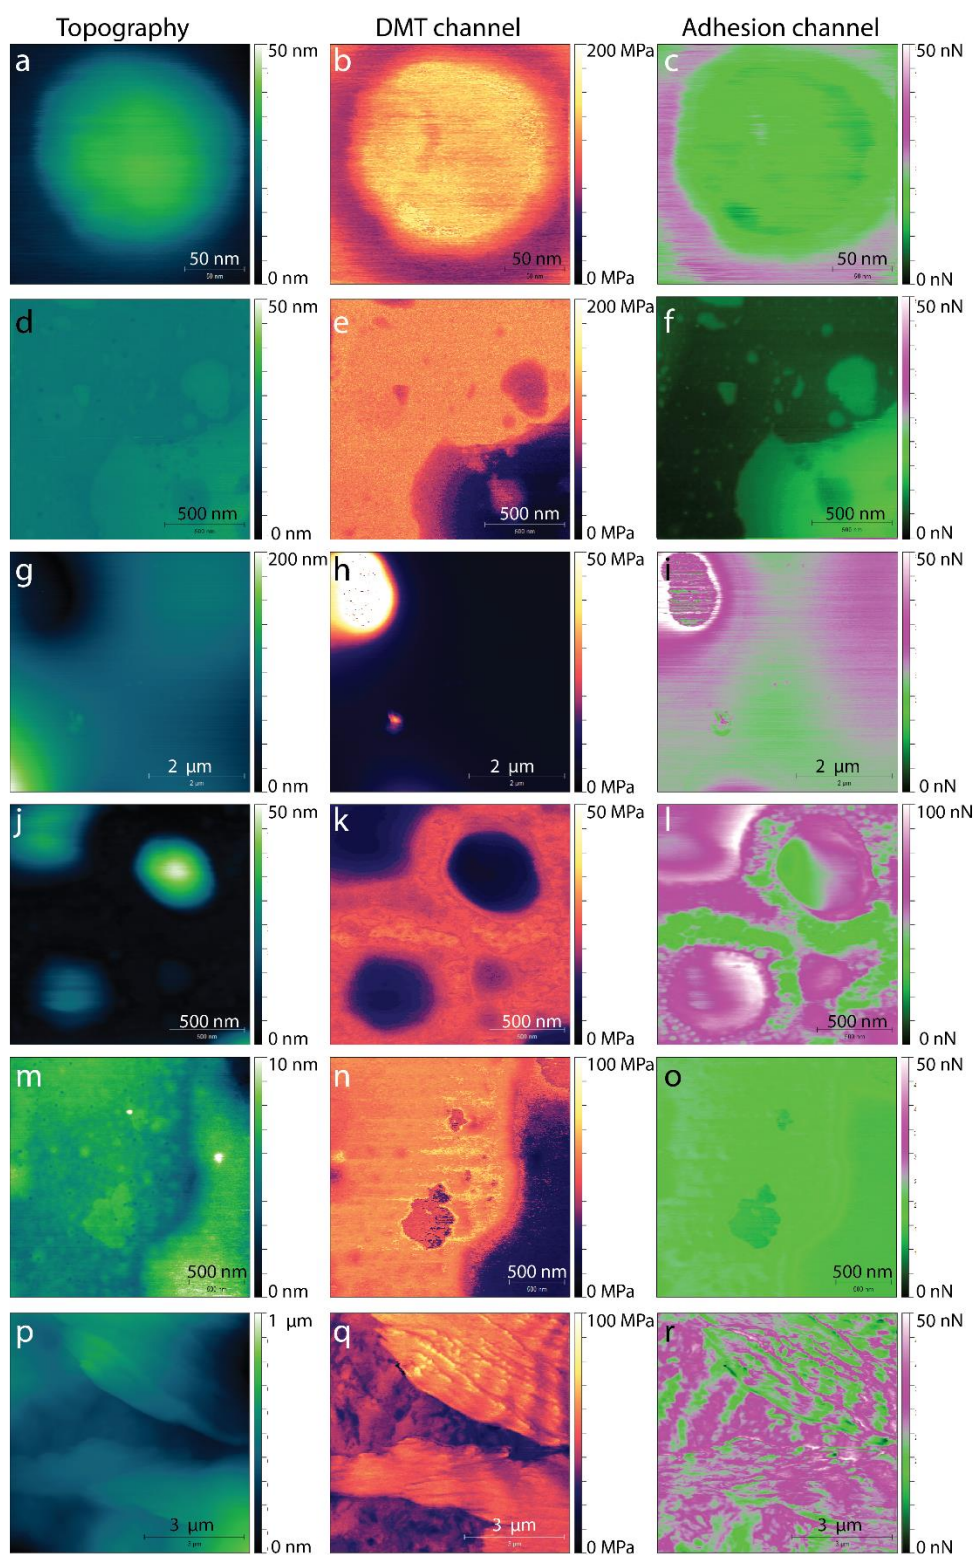


Figure S14. AFM images of (a - c) PGA, (d - f) PGAB 11%, (g - i) PGAB 60%, (j - l) PGAB 75%, (m - o) PGO 65%, and (p - r) PGAS 65%, with left-most column from height channel, central column from DMT (stiffness) channel, and right-most column from adhesion channel.

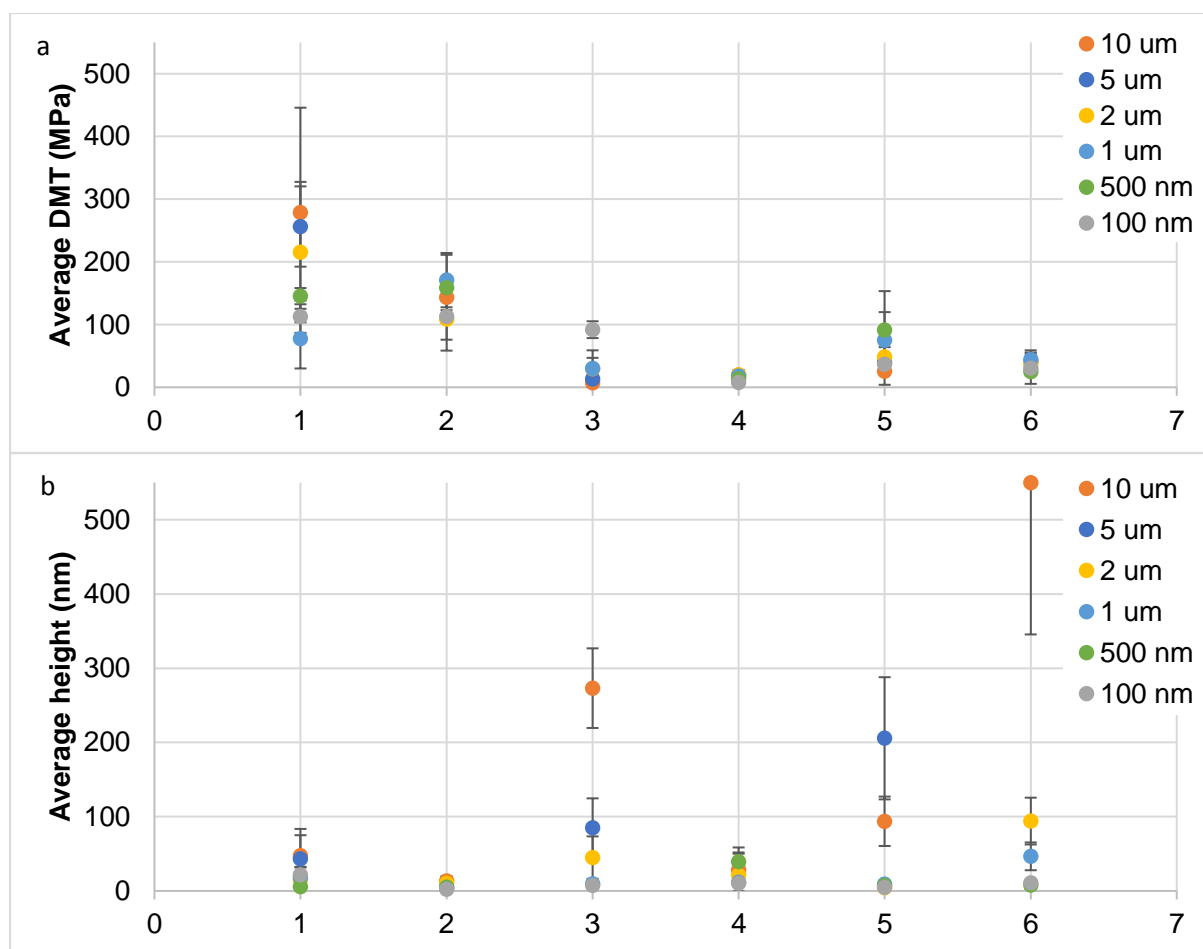



Figure S15. DMT (stiffness, a) and height (topography, b) and values extracted from QNM images of varying image area size. Each data point is an average of the entire scan area, with the RMS (rq) used for standard deviation. Samples 1– 6 are PGA, PGAB 11%, PGAB 60%, PGAB 75%, PGO 65%, and PGAS 65%, respectively.

AFM statistical analyses:

AFM images were analysed using freeware Gwyddion (v2.41, <http://gwyddion.net>). For height data, plane subtraction and line correction were carried out, and minimum height was set to zero. For adhesion and DMT data, no data correction was applied. Samples showing a strong topographical artefact were excluded. The 'statistical quantities' function was utilised to obtain the average and RMS (rq) values across entire images (512 x 512 pixels) and exported to Excel. Where multiple images of one scale were available, data was averaged and the error was calculated as the square root of the average variance. These data are tabulated as follows where N = number of images used:


		10000 nm			5000 nm			2000 nm		
		height (nm)	DMT (MPa)	Adhesion (nN)	height (nm)	DMT (MPa)	Adhesion (nN)	height (nm)	DMT (MPa)	Adhesion (nN)
PGA	mean	47.49	278.97	29.59	43.41	256.41	28.50	15.08	215.59	23.07
	deviation	36.1	166.9	8.3	41.4	64.0	5.9	9.4	112.0	8.4
	N	2			2			3		
PGAB 11%	mean	13.55	143.61	7.01				10.33	108.88	6.86
	deviation	6.8	67.7	4.7				11.1	50.4	4.4
	N	3						3		
PGAB 60%	mean	273.15	7.13	27.82	84.93	13.12	28.42	44.91	29.38	22.44
	deviation	53.9	11.3	4.8	40.5	15.8	7.5	28.6	29.6	4.8
	N	2			2			1		
PGAB 75%	mean	28.52	19.23	59.84				21.32	20.09	62.01
	deviation	30.1	7.6	14.2				30.5	7.2	14.0
	N	1						3		
PGAO 65%	mean	93.85	25.79	17.19				4.62	48.47	14.84
	deviation	41.1	21.8	3.8				2.4	15.6	2.1
	N	2						3		
PGAS 65%	mean	549.90	41.26	20.27	205.63	39.77	20.12	94.14	38.39	24.35
	deviation	204.4	12.2	6.0	82.3	10.0	7.0	33.2	9.0	5.3
	N	1			1			2		

		1000 nm			500 nm			100 nm		
		height (nm)	DMT (MPa)	Adhesion (nN)	height (nm)	DMT (MPa)	Adhesion (nN)	height (nm)	DMT (MPa)	Adhesion (nN)
PGA	mean	18.32	77.62	31.60	5.84	145.37	18.39	21.90	112.60	20.23
	deviation	14.2	47.6	9.4	21.0	12.9	2.4	9.7	25.8	4.2
	N	1			3			1		
PGAB 11%	mean	5.11	170.91	5.89	4.87	158.89	3.65	2.14	113.05	4.68
	deviation	1.2	43.3	2.3	0.5	12.4	1.0	0.9	9.9	1.2
	N	1			2			1		
PGAB 60%	mean	9.51	29.88	22.96				7.30	91.90	33.15
	deviation	4.1	17.1	2.7				2.3	13.4	5.4
	N	2						3		
PGAB 75%	mean	11.60	18.02	59.62	39.24	13.11	50.43	10.71	7.65	46.13
	deviation	12.3	5.8	15.1	11.5	4.8	11.2	2.5	0.5	2.1
	N	2			2			1		
PGAO 65%	mean	9.24	74.89	12.18	7.34	91.38	14.23	5.04	36.62	11.45
	deviation	3.8	45.0	2.1	3.9	62.0	3.1	1.9	13.2	1.7
	N	3			1			2		
PGAS 65%	mean	46.64	44.67	7.91	7.73	24.87	38.78	11.07	30.49	1.47
	deviation	20.6	14.3	2.0	5.1	5.6	4.4	3.3	25.0	0.4
	N	4			1			1		

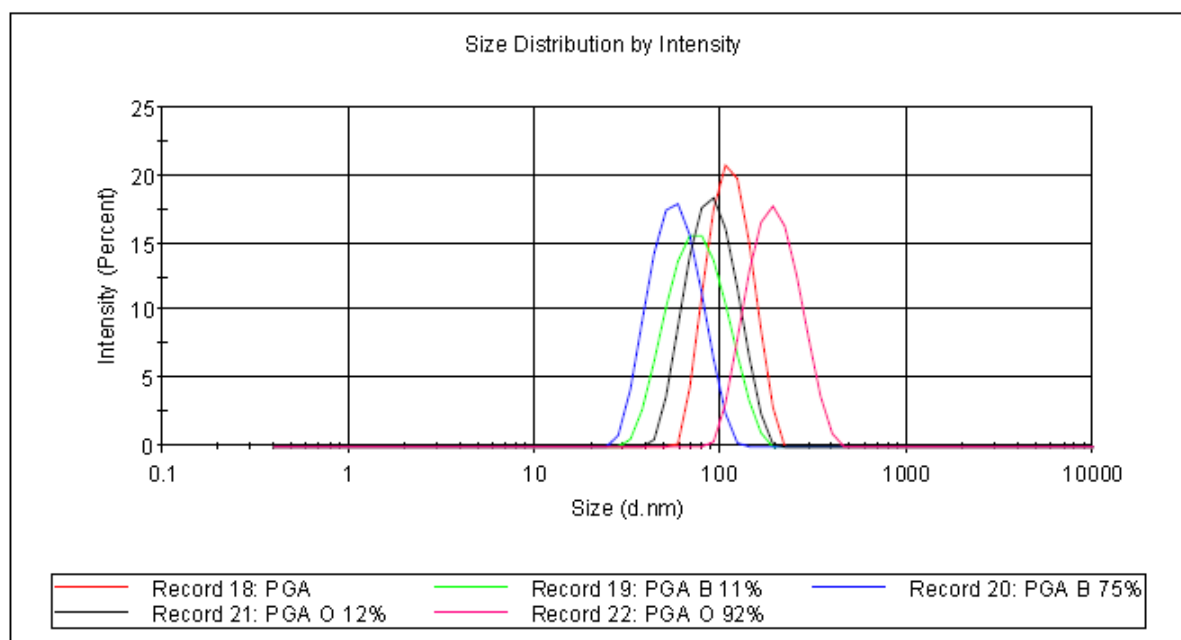


PGA

	Size (d.nm):	% Intensity:	St Dev (d.nm):
Z-Average (d.nm): 108.0	Peak 1: 114.6	100.0	29.21
PdI: 0.043	Peak 2: 0.000	0.0	0.000
Intercept: 0.917	Peak 3: 0.000	0.0	0.000
Result quality : Good			

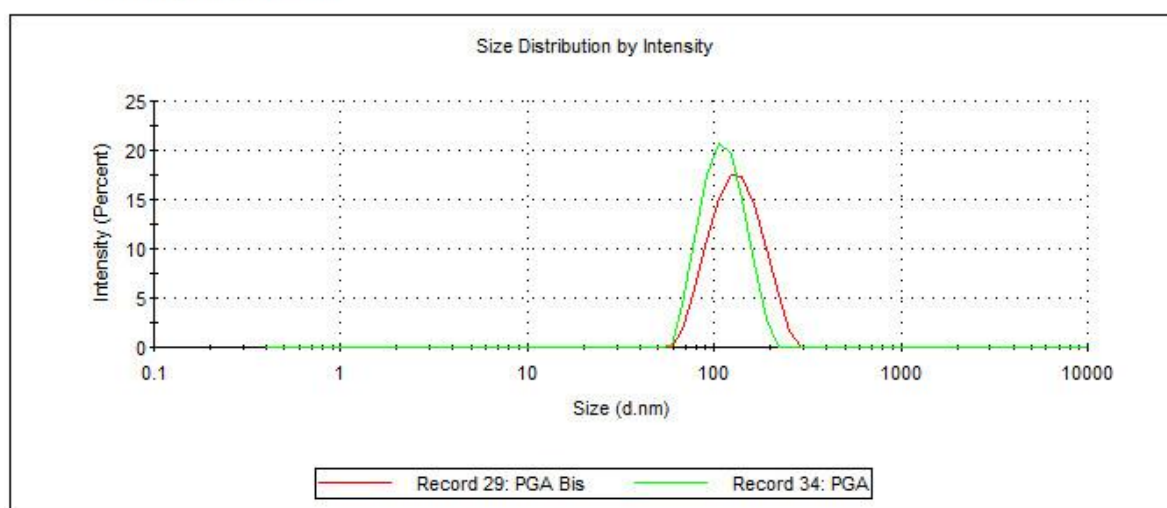


	Size (d.nm):	% Volume:	St Dev (d.nm):
Z-Average (d.nm): 108.0	Peak 1: 102.0	100.0	29.63
Pdl: 0.043	Peak 2: 0.000	0.0	0.000
Intercept: 0.917	Peak 3: 0.000	0.0	0.000

Result quality : Good

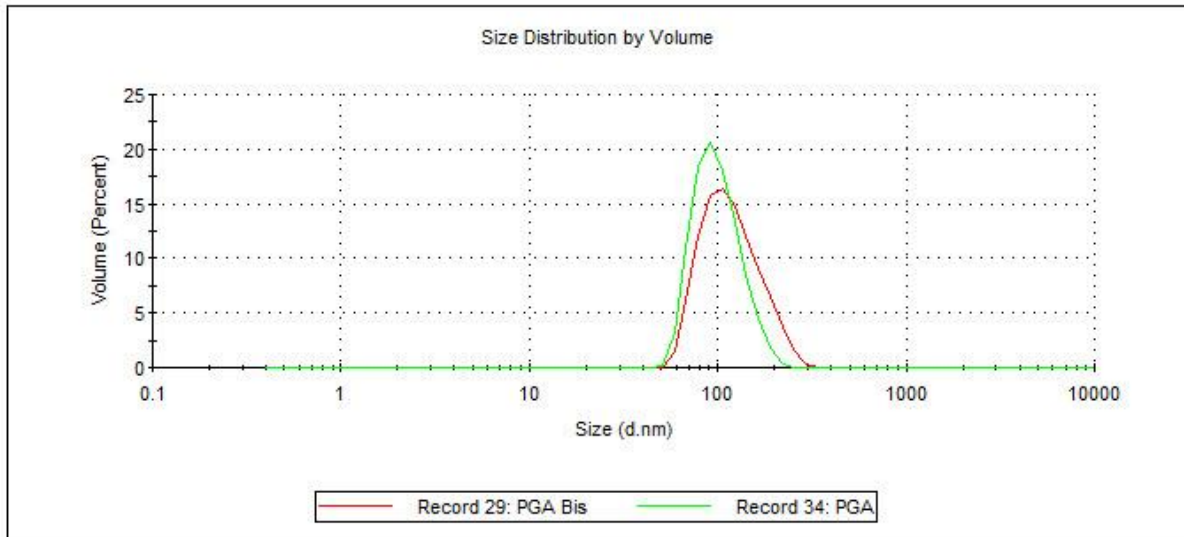


	Size (d.nm):	% Number:	St Dev (d.nm):
Z-Average (d.nm): 108.0	Peak 1: 85.93	100.0	21.38
Pdl: 0.043	Peak 2: 0.000	0.0	0.000
Intercept: 0.917	Peak 3: 0.000	0.0	0.000

Result quality : Good

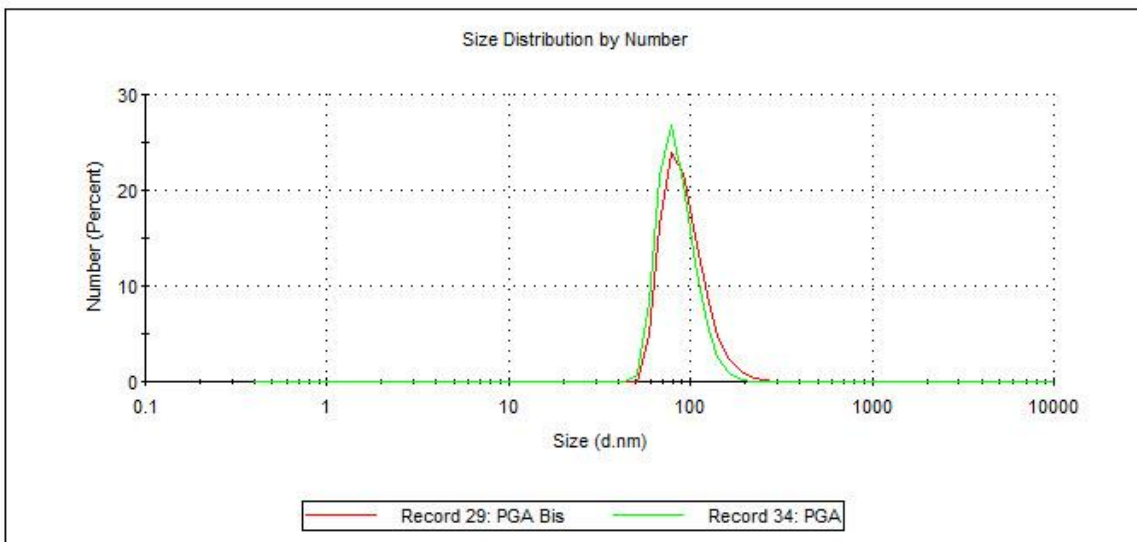


PGAB11

	Size (d.nm):	% Intensity:	St Dev (d.nm):
Z-Average (d.nm): 70.35	Peak 1: 77.96	100.0	25.38
Pdl: 0.089	Peak 2: 0.000	0.0	0.000
Intercept: 0.935	Peak 3: 0.000	0.0	0.000
Result quality : Good			

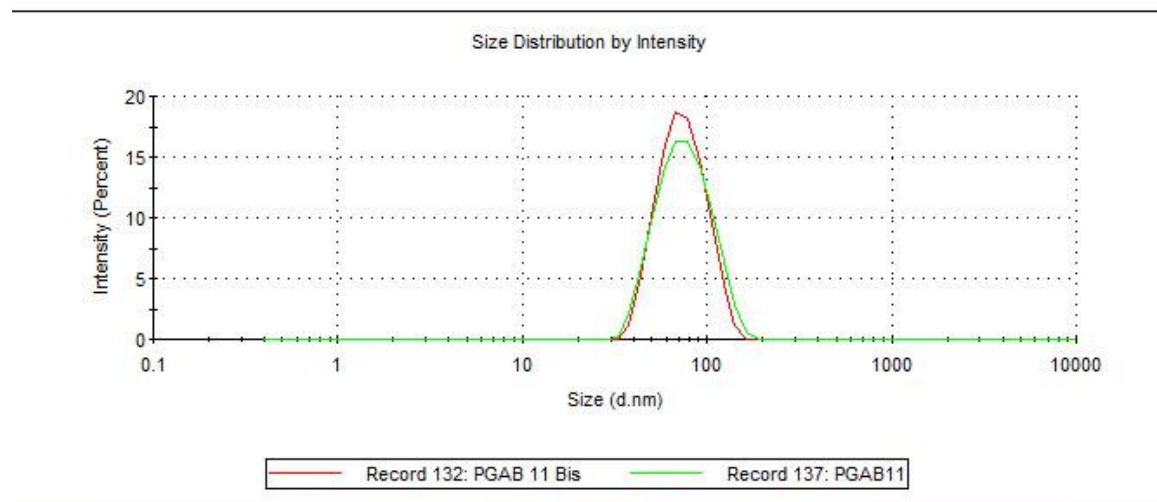


	Size (d.nm):	% Volume:	St Dev (d.nm):
Z-Average (d.nm): 70.35	Peak 1: 60.44	100.0	20.71
Pdl: 0.089	Peak 2: 0.000	0.0	0.000
Intercept: 0.935	Peak 3: 0.000	0.0	0.000
Result quality : Good			

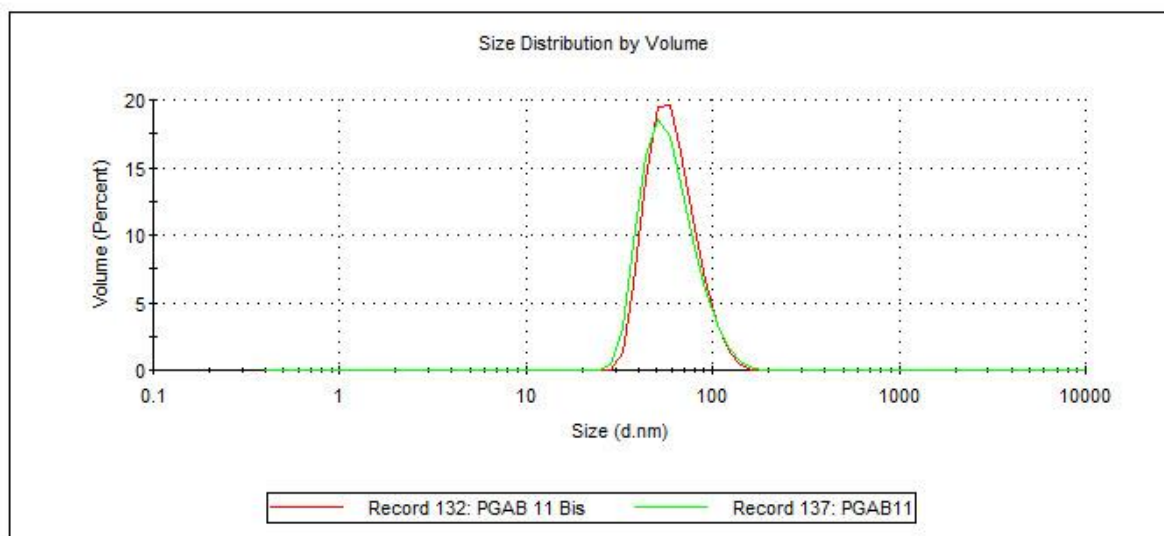


	Size (d.nm):	% Number:	St Dev (d.nm):
Z-Average (d.nm): 70.35	Peak 1: 48.36	100.0	13.23
Pdl: 0.089	Peak 2: 0.000	0.0	0.000
Intercept: 0.935	Peak 3: 0.000	0.0	0.000

Result quality : **Good**

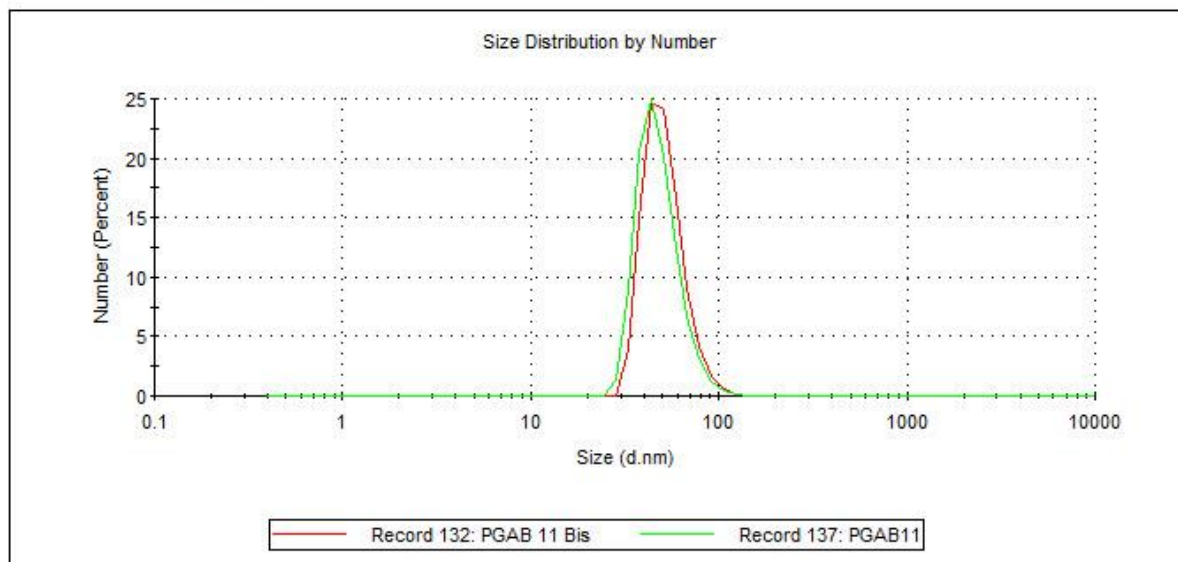


PGAO65

	Size (d.nm):	% Intensity:	St Dev (d.nm):
Z-Average (d.nm): 128.7	Peak 1: 141.6	100.0	44.63
Pdl: 0.094	Peak 2: 0.000	0.0	0.000
Intercept: 0.948	Peak 3: 0.000	0.0	0.000
Result quality : Good			

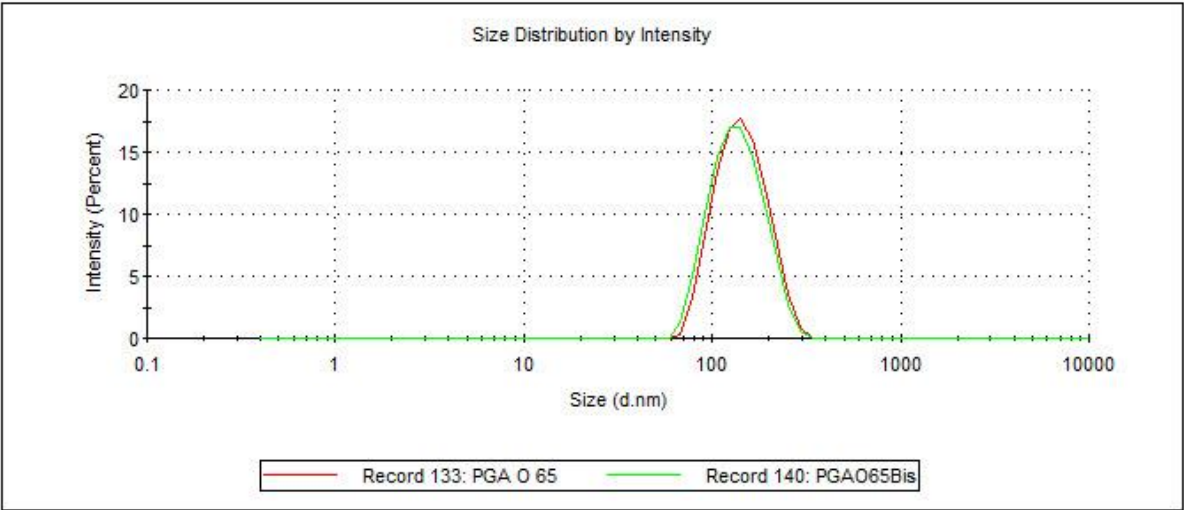


	Size (d.nm):	% Volume:	St Dev (d.nm):
Z-Average (d.nm): 128.7	Peak 1: 126.3	100.0	46.57
Pdl: 0.094	Peak 2: 0.000	0.0	0.000
Intercept: 0.948	Peak 3: 0.000	0.0	0.000
Result quality : Good			

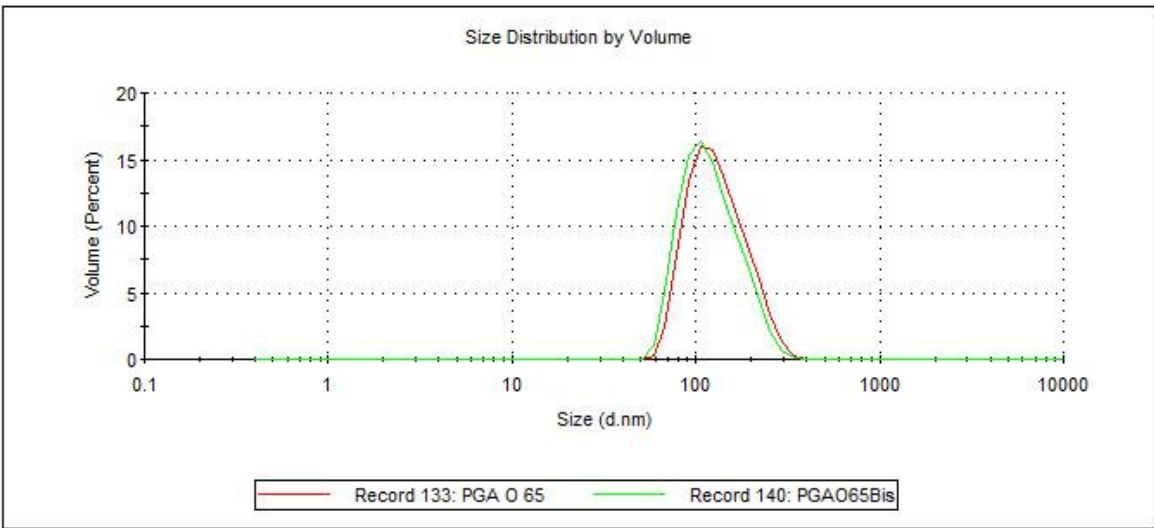


	Size (d.nm):	% Number:	St Dev (d.nm):
Z-Average (d.nm): 128.7	Peak 1: 96.14	100.0	28.63
Pdl: 0.094	Peak 2: 0.000	0.0	0.000
Intercept: 0.948	Peak 3: 0.000	0.0	0.000

Result quality : **Good**

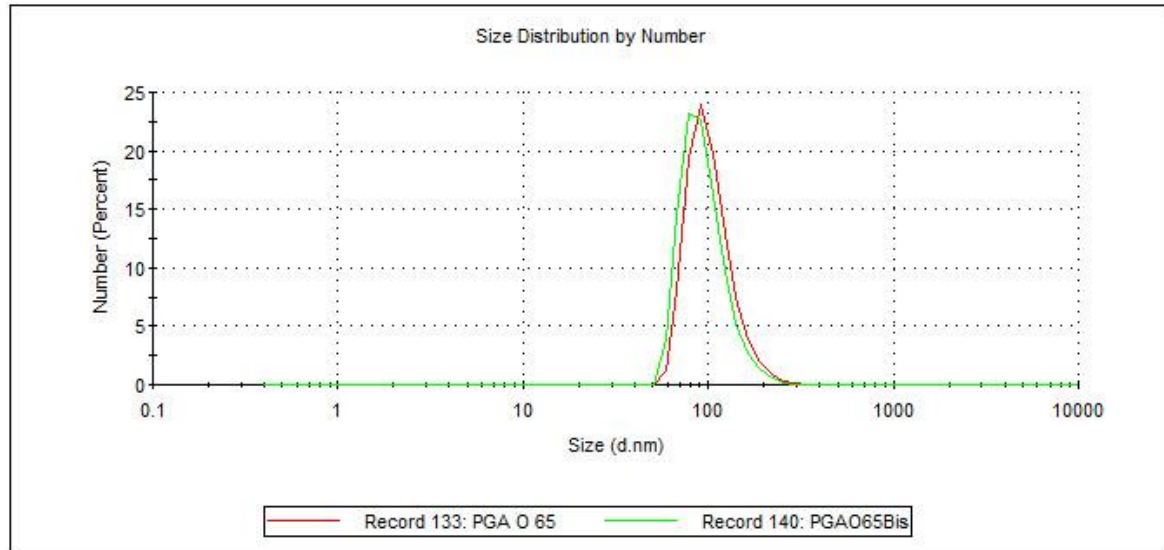


PGAS14

	Size (d.nm):	% Intensity:	St Dev (d.nm):
Z-Average (d.nm): 140.1	Peak 1: 110.9	78.0	40.95
Pdl: 0.467	Peak 2: 935.7	13.4	293.4
Intercept: 0.891	Peak 3: 4883	8.6	688.9
Result quality : Good			

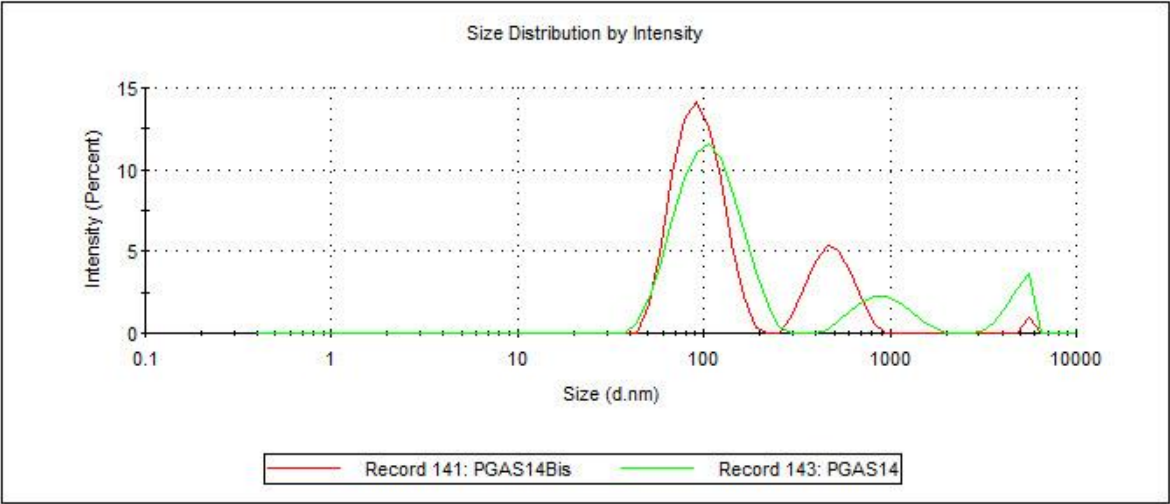

	Size (d.nm):	% Volume:	St Dev (d.nm):
Z-Average (d.nm): 140.1	Peak 1: 84.54	68.2	36.33
Pdl: 0.467	Peak 2: 1093	23.0	298.1
Intercept: 0.891	Peak 3: 5137	8.8	807.8
Result quality : Good			

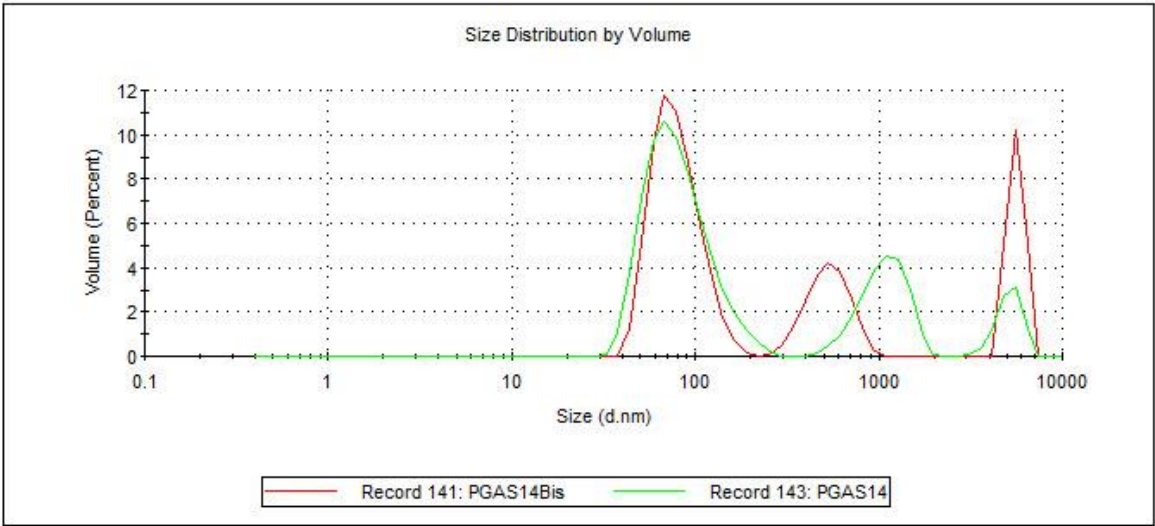

	Size (d.nm):	% Number:	St Dev (d.nm):
Z-Average (d.nm): 140.1	Peak 1: 60.87	100.0	19.31
Pdl: 0.467	Peak 2: 861.2	0.0	275.5
Intercept: 0.891	Peak 3: 0.000	0.0	0.000

Result quality : Good

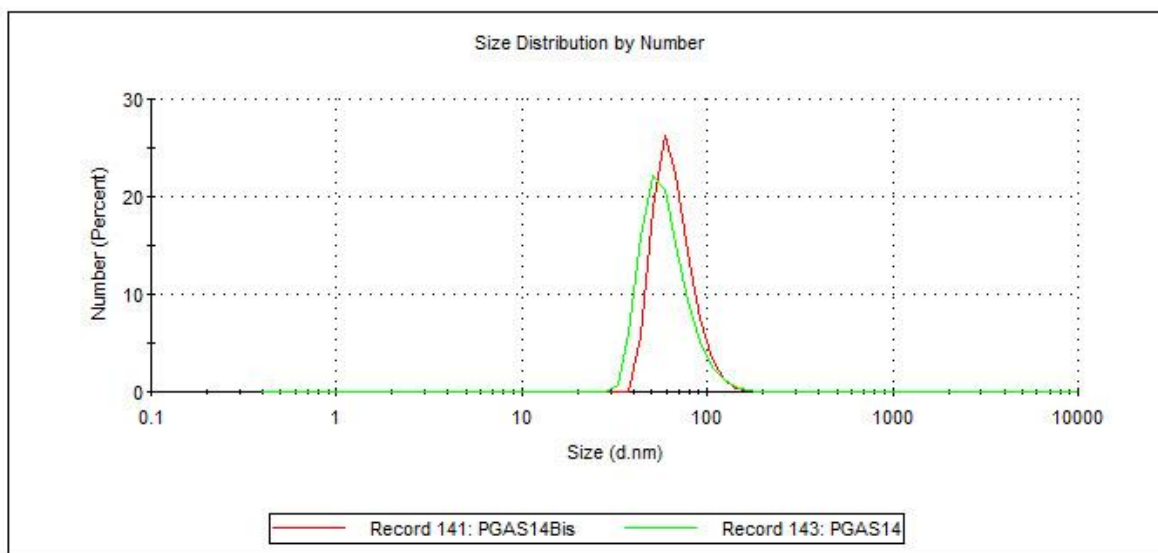


Figure SI6a DLS traces of PGA, PGO12, PGAB11, PGO92 and PGAB75, PGAS14 and PGO65. Intensity, volume and number traces.

Results

	Size (d.n...	% Intensity	St Dev (d.n...
Z-Average (d.nm): 140.1	Peak 1: 110.9	78.0	40.95
Pdl: 0.467	Peak 2: 935.7	13.4	293.4
Intercept: 0.891	Peak 3: 4883	8.6	688.9
Result quality Good			

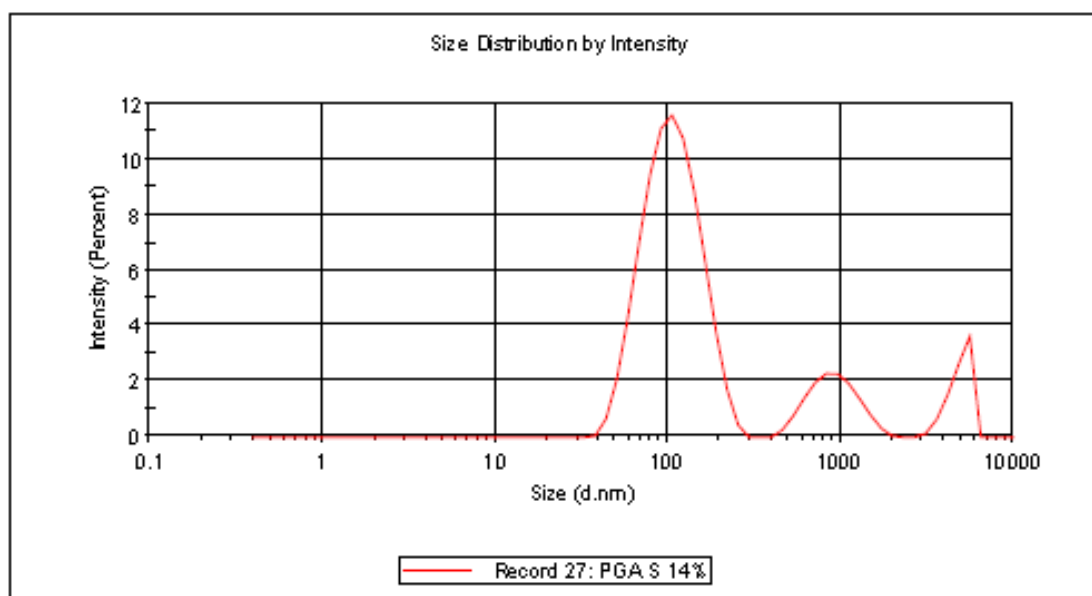


Figure SI6b. DLS intensity trace of PGAS14

Results

	Size (d.n...	% Intensity	St Dev (d.n...
Z-Average (d.nm): 127.7	Peak 1: 116.7	94.2	38.96
Pdl: 0.348	Peak 2: 5163	5.8	497.8
Intercept: 0.930	Peak 3: 0.000	0.0	0.000
Result quality Good			

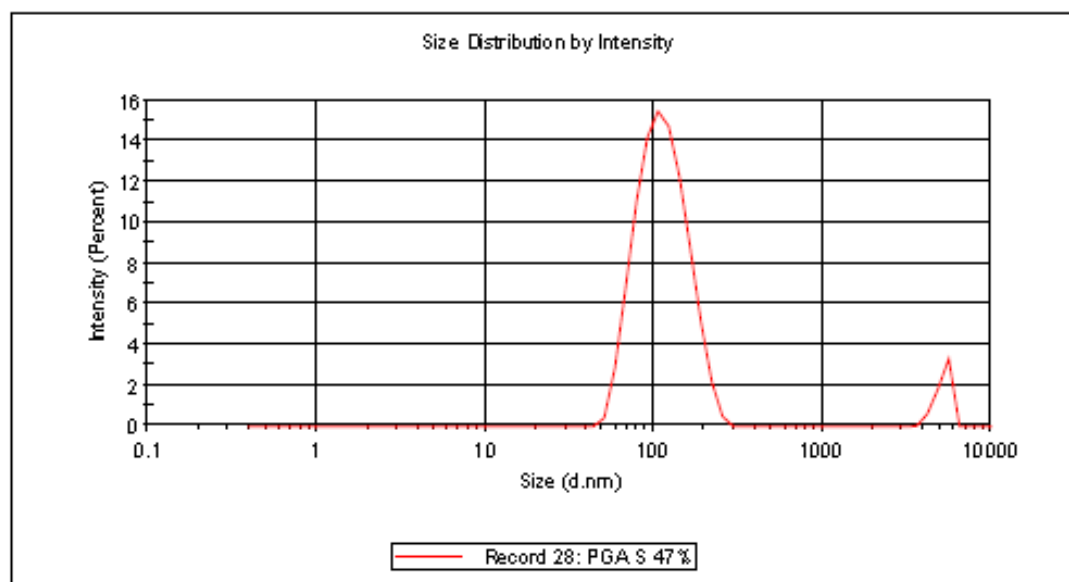


Figure SI6b. PGAS47 DLS trace.

Results

	Size (d.n...	% Intensity	St Dev (d.n...
Z-Average (d.nm): 136.0	Peak 1: 144.3	100.0	36.65
Pdl: 0.045	Peak 2: 0.000	0.0	0.000
Intercept: 0.946	Peak 3: 0.000	0.0	0.000
Result quality Good			

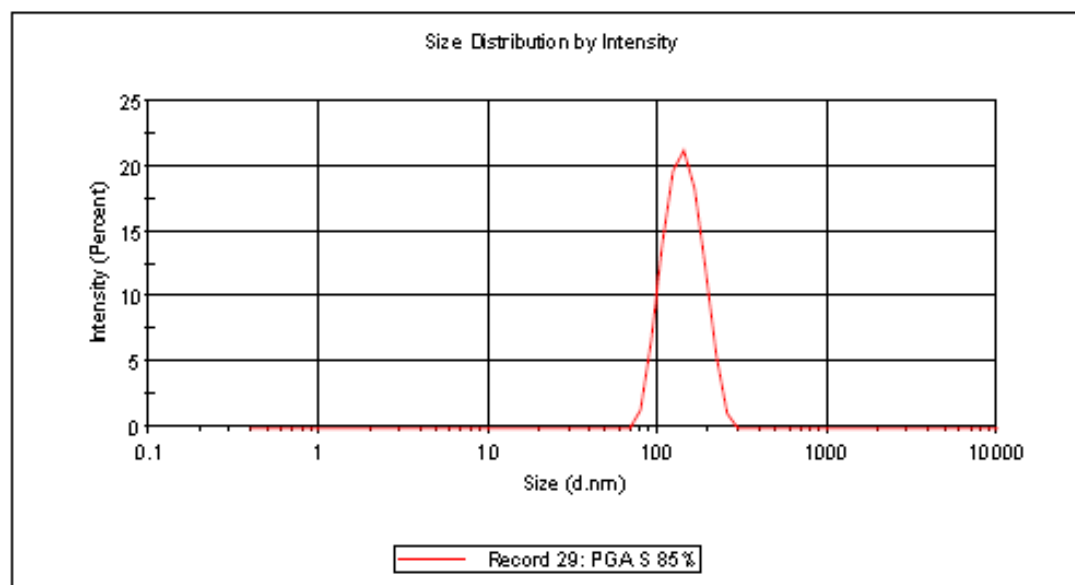


Figure SI6b. DLS Intensity trace of PGAS85.